

Weak inter-band coupling in Mg^{10}B_2 : a specific heat analysis

A. Wälte^{1,*}, S.-L. Drechsler¹, G. Fuchs¹, K.-H. Müller¹, K. Nenkov^{1,2}, D. Hinz¹, and L. Schultz¹

¹*IFW Dresden, Institute for Metallic Materials, P.O. Box 270116, D-01171 Dresden, Germany*

²*International Laboratory for High Magnetic fields and Low Temperatures, 95 Gajowicka Str., 53 421 Wrocław, Poland*

(Dated: February 2, 2008)

The superconducting state of Mg^{10}B_2 is investigated by specific heat measurements in detail. The specific heat in the normal state is analyzed using a recently developed computer code. This allows for an extraction of the electronic specific heat in the superconducting state with high accuracy and a fair determination of the main lattice features. One of the two investigated samples shows a hump in the specific heat at low temperatures within the superconducting state, accompanied by an unusual low value of the small gap, $\Delta_\pi(0) = 1.32$ meV, pointing to a very weak inter-band coupling. This sample allows for a detailed analysis of the contribution from the π -band to the electronic specific heat in the superconducting state. Therefore the usual analysis method is modified, to include the individual conservation of entropy of both bands. From analyzing the deviation function $D(t)$ of MgB_2 , the theoretically predicted weak inter-band coupling scenario is confirmed.

PACS numbers: 74.70.Ad, 74.25.Bt, 74.25.Kc

I. INTRODUCTION

The discovery¹ of the unexpected high $T_c \approx 39$ K of MgB_2 was surprising for such a simple binary system and has motivated much experimental and theoretical work in order to understand the physics behind this superconductor. It turned out that the electronic structure exhibits two bands crossing the Fermi level. However from the relatively small electronic density of states $N(0) \approx 0.71$ states/(eV · unit-cell) at the Fermi level,^{2,3,4,5,6} one would not expect a notable T_c . Nowadays it is generally accepted that the high energy vibrations here play the crucial role.^{7,8,9,10,11,12} A closer examination of the electronic structure revealed an almost decoupled state of the two prominent bands, with the π -band contributing $\approx 57\%$ and the σ -band $\approx 43\%$ to the total density of states.^{13,14} Considerable effort was done to quantify the role of these two bands for the superconductivity from theory and experiment (for a review see Ref. 12). The specific heat of the superconducting state is usually analyzed in terms of a linear combination of two α -models, with one energy gap above and one below the BCS limit. Recently Dolgov et al. compared this approach to a two-band Eliashberg approach and found it adequate particularly for the case of enhanced inter-band scattering.¹⁵ The effect of different inter-band scattering rates was analyzed by Nicol and Carbotte, likewise based on two-band Eliashberg calculations. These authors predict the visibility of a jump at $\approx 0.2T/T_c$, where the order parameter of the π -band is expected to change strongest.¹⁶

In the present work we present the specific heat analysis of a Mg^{10}B_2 -sample, showing a small upturn in the same temperature region, indicating a reduced inter-band coupling compared to so far published data. A recently developed computer code for the analysis of lattice dynamics from specific heat measurements in the normal state is used in order to extract the specific heat in the superconducting state with high accuracy. With respect

to the relatively low inter-band coupling within MgB_2 a slightly different approach to the superconducting state is suggested. It involves one α -model to describe the jump height of the specific heat at T_c using the condition of entropy-conservation between $0 < T < T_c$. Consequently the remaining electronic specific heat in the superconducting state can be ascribed to the phase-transition of the second band.

II. EXPERIMENTAL

Polycrystalline samples of Mg^{10}B_2 have been prepared by solid-state reaction and a subsequent hot-pressure treatment. To prepare the sample, a mixture of Mg and ^{10}B powder was pressed into a pellet, wrapped in Ta foil and sealed in a quartz ampoule containing an Ar atmosphere at 180 mbar. The sample was sintered for 2 hours at 950 °C. In order to obtain samples with high T_c -values additional 10 % B was used. To counter the high volatility of Mg, an additional small piece of pure Mg was placed in the ampoule. The hot-pressure treatment is necessary to reduce the porousness of the derived sample. The obtained dense samples were characterized by x-ray diffractometry to estimate their quality. No second phase peaks occurred, indicating that even the contribution of the usually forming MgO is negligible. The superconducting transition temperature (onset) $T_c = 40.2$ K measured by ac-susceptibility is in agreement with so far published values for Mg^{10}B_2 .^{17,18} The specific heat was measured in the temperature range of $0.3 < T < 200$ K and in magnetic fields up to $\mu_0 H = 9$ T using a Quantum Design Physical Property Measurement System. In the following analysis we denote the sample showing the low-temperature upturn with “A” and the piece not showing this anomaly with “B”.

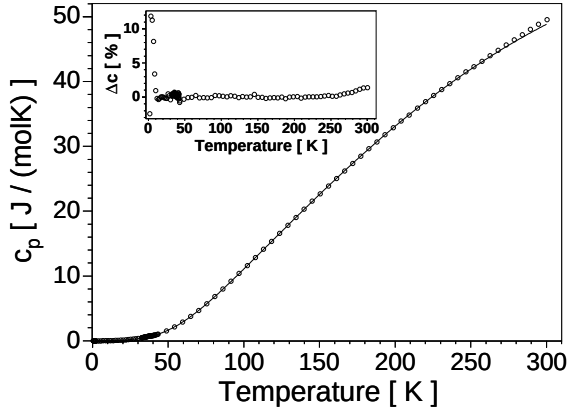


FIG. 1: Specific heat of Mg^{10}B_2 . Solid line: model fit (see text for details). The superconducting transition is too small to be visible in this plot. Inset: relative difference between data and model (zero field data above T_c and $\mu_0 H = 9$ T-data below T_c). The large deviation of $\approx 10\%$ at low temperatures can be ascribed to the superconducting transition which is not fully suppressed at $\mu_0 H = 9$ T.

III. RESULTS AND ANALYSIS

The specific heat of MgB_2 was analyzed in several experimental works before. One crucial point in these analyses is the determination of the Sommerfeld parameter, which is usually extracted by measuring the specific heat in magnetic fields, which destroy the superconducting state. However, analyses based on this approach can result in difficulties concerning the conservation of entropy of the superconducting state,¹⁹ which is also visible in other quantities like the deviation function.¹⁶ It is unclear, if this is due to the experimental error,¹⁹ remnants of the superconducting signature of the field-measurements²⁰ or perhaps due to a field-dependent Schottky anomaly, which is reported for some samples including the present one.

In order to minimize such uncertainties we decided to apply a new computer code to analyze the normal state of the specific heat in a larger temperature region. The main ideas of the code have been sketched in a previous work.²¹ A more detailed description will be published elsewhere. In summary our computer code makes use of a linear combination of the well known Einstein and Debye models for the specific heat in the normal state. The usual procedure in fitting specific heat data using this code is to vary the Sommerfeld parameter until the fit quality is optimized.

A. Specific heat in the normal state

The specific heat of the investigated Mg^{10}B_2 sample A is shown in Fig. 1. To extract the electronic specific

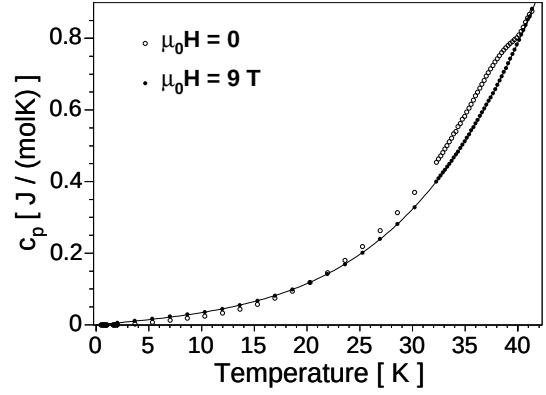


FIG. 2: Specific heat of Mg^{10}B_2 at low temperatures. Solid line: Model of the normal state specific heat (see text for details).

heat in the superconducting state, one has to determine the Sommerfeld parameter and the lattice part. For this purpose the zero-field data and $\mu_0 H = 9$ T data measured down to $T = 20$ K were used. The application of the mentioned computer code indicated additional anharmonic effects starting at $T \approx 250$ K. Therefore the fitting temperature range of the computer code was restricted to $20 < T < 250$ K. To increase the accuracy of the fit, the conservation of entropy of the superconducting transition was used as an additional requirement for a successful fit. The Sommerfeld parameter was varied using a step-size of $0.005 \text{ mJ} / (\text{molK}^2)$ until the deviation between the data and the fitted curve was minimized and the entropy of the superconducting transition was conserved. At temperatures below ≈ 4 K one has also to account for hyperfine structure contributions,^{22,23,24} given by a Schottky model

$$c_s(T) = x \frac{Z \sum_i L_i^2 \exp(L_i/T) - [\sum_i L_i \exp(L_i/T)]^2}{(TZ)^2},$$

with partition function $Z = \sum_i [\exp(L_i/T)]^{-1}$, eigenvalues $L_i = \Delta_i/k_B$ and concentration x of paramagnetic particles. The specific heat model is then given by $c_p(T) = \gamma_N T + c_{\text{lattice}}(T) + c_s(T)$. The result of the fitting procedure is shown as black line in Fig. 1. The inset shows the difference between the data and the model, which is well below 1 % except for low temperatures, indicating that there the superconducting signature is not fully suppressed by the applied 9 T-field. Piece B shows nearly the same data-to-model-difference which is not shown here.

Fig. 2 shows the specific heat of sample A at $H = 0$ and $\mu_0 H = 9$ T in the low temperature region. The very good agreement between the model and the field measurement is visible. The Sommerfeld parameter converged to $\gamma_N = 2.69 (1 \pm 0.004) \text{ mJ} / (\text{molK}^2)$, agreeing well with published values of high quality samples, rang-

TABLE I: Phonon-related parameters as obtained from the normal state specific heat analysis. Numbering according to Fig. 3.

		acoustic –		optical modes				
		D1	D2	E1	E2	E3	E4	E5
ω	[meV]	50.8	78.9	15.9	29.4	42.2	84.2	86.7
ν_i		2	1	0.05	1	1	2	1.95

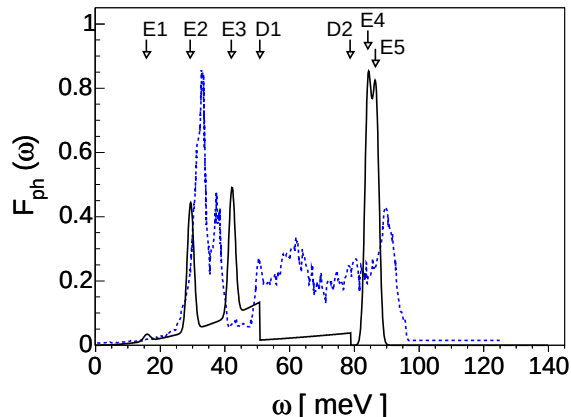


FIG. 3: (Color online) Phonon density of states. Black line: result from the specific heat analysis. Dashed line: calculated PDOS taken from Ref. 8 (scaled to the peak value of the present result). Numberings according to Tab. I.

ing from $\gamma_N \approx 2.5 - 2.7$ mJ/(molK²).^{19,22,23,24}

Using the bare electron parameter $\gamma_0 = \pi^2 k_B^2 N(0)/3 = 1.67$ mJ/(molK²), the mean electron-phonon coupling constant can be calculated from the mass enhancement relation

$$\gamma_N = \gamma_0 (1 + \bar{\lambda}_{ph}) \quad (1)$$

as $\bar{\lambda}_{ph} \approx 0.61$. The mean electron-phonon coupling constant is related to the partial coupling constants in the σ - and π -band by

$$\bar{\lambda}_{ph} = \lambda_{ph,\sigma} \frac{\gamma_{0,\sigma}}{\gamma_0} + \lambda_{ph,\pi} \frac{\gamma_{0,\pi}}{\gamma_0}. \quad (2)$$

From fitting the Schottky contribution $c_s(T)$ a concentration of $x = 4.25 \times 10^{-4}$ mol of paramagnetic particles with two energy levels, $\Delta_1 \approx 0.014$ meV and $\Delta_2 \approx 0.453$ meV is estimated, probably due to small amounts of Fe-impurities.^{23,24} However a quantitative analysis of the energy levels requires measurements below $T \approx 0.3$ K, where the normal state contributions vanish.

The derived phonon-related parameters are summarized in Tab. I. The resulting phonon density of states (PDOS) of sample A is shown in Fig. 3 in comparison with a calculated PDOS taken from Ref. 8. The nice agreement, in particular of the prominent modes at ≈ 30 meV and ≈ 85 meV (E_{2g}) shows, that our computer code is able to extract the main features of the

phonon density of states from specific heat measurements independently. A similar agreement is found from comparing the specific heat derived PDOS with the generalized density of states measured by neutron scattering experiments.^{8,9,11}

B. Specific heat in the superconducting state

Fig. 4 shows the specific heat below $T = 43$ K after subtraction of the normal state contribution for the two investigated samples A and B. The idealized specific heat jump of $\Delta c = 103.35$ mJ/(molK) for sample A is in the range of reported values, ranging from $\Delta c = 81$ (Ref. 24) to 133 mJ/(molK).²² The local maximum at $T \approx 9$ K found for piece A has not been reported before. The measurement was repeated on that piece and the small hump is found to be reproducible. Piece B from the same initial sample does not show this hump, but a much more broadened feature (open circles). Most probably the observed hump is related to a relatively weak coupling between the two bands (a more detailed analysis including magnetic field dependence is presented in section III C).^{16,25} In view of the two-band properties of MgB₂ it is more illustrative to continue the analysis of piece A.

Assuming a very weak inter-band coupling, the jump at T_c is nearly completely due to the σ -band which is responsible for the large T_c . Consequently one α -model was used to fit the jump at $T_{c,\sigma} = 39.0$ K using an entropy-conserving condition. This unambiguously results in a Sommerfeld parameter $\gamma_{N,\sigma} \approx 1.44$ mJ/(molK²) of the σ -band, avoiding any uncertainty in the correct partitioning of the Sommerfeld parameter under the two bands (see Ref. 26 for a short summary). The gap ratio amounts $2\Delta_\sigma(0)/(k_B T_{c,\sigma}) = 3.98$, resulting in $\Delta_\sigma(0) = 6.70$ meV.

Fig. 5 shows the entropy difference of the electrons between the normal and the superconducting state. The solid line represents the entropy difference of the experimental data, agreeing well with results obtained by Yang et al.²³ The dashed line is the entropy difference of the fitted α -model and the dotted line corresponds to the residual entropy difference which can be attributed to the π -band. The superconducting transition of the π -electrons is strongly smeared due to the inter-band coupling, but the main part of the π -electrons seems to become superconducting at $T_c^* \approx 9$ K, otherwise the minimum in the entropy difference (dotted line) would be expected at higher temperatures. This interpretation does not mean that the gap of the π -band also opens at T_c^* . In fact, any strength of inter-band coupling results in one single critical temperature $T_{c,\sigma}$ for both gaps. However the order parameter of the π -band is expected to show its strongest change around T_c^* .¹⁶

Fig. 6 shows the specific heat $\Delta c^*/T$ in the superconducting state of sample A (filled circles) after subtraction of the σ -band contribution given by the α -model (see Fig.

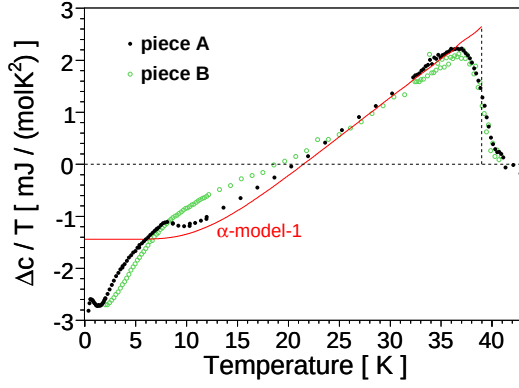


FIG. 4: (Color online) Electronic specific heat $\Delta c/T$ of Mg^{10}B_2 in the superconducting state. Symbols: data of piece A. Broad line: data of piece B. Solid line marked with “ α -model-1”: α -model fitted to the jump of piece A satisfying the condition of entropy-conservation.

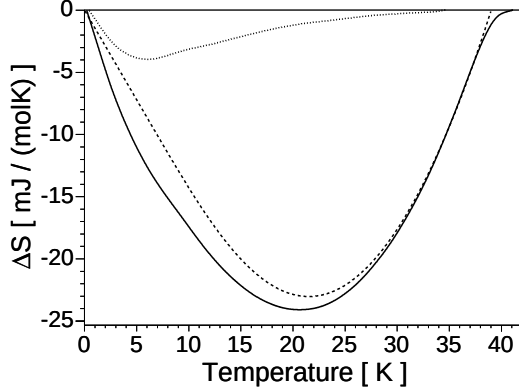


FIG. 5: Entropy difference between the normal and superconducting state of sample A. Solid line: entropy difference determined from the electronic specific heat. Dashed line: entropy difference of the fitted α -model. Dotted line: residual entropy difference.

4). The Sommerfeld parameter of the π -band amounts $\gamma_{N,\pi} = \gamma_N - \gamma_{N,\sigma} = 1.25 \text{ mJ} / (\text{molK}^2)$. The small deviations for $T < 2 \text{ K}$ can be attributed to the inexact knowledge of the Schottky contribution, which should be determined at much lower temperatures. However the accuracy is sufficient for the present analysis. A second α -model was applied to the remaining specific heat, using $T_c^* \approx 9 \text{ K}$. Since the superconducting transition of the π -electrons is strongly smeared (up to $T_{c,\sigma}$), reliable results on the energy gap can be derived only from the low temperature tail. Using $\gamma_N = \gamma_{N,\pi}$ and $T_c^* = 8.7 \text{ K}$ the solid line shown in Fig. 6 (marked by “ α -model-2”) is derived. The resulting gap amounts $\Delta_\pi(0) = 1.32 \text{ meV}$ with the BCS gap ratio $2\Delta_\pi(0) / (k_B T_c^*) = 3.52$. This value is much smaller than reported from other specific

TABLE II: Gap values obtained from the α -model for the two investigated samples.

Sample	$\Delta_\sigma [\text{meV}]$	$\Delta_\pi [\text{meV}]$	$T_{c,\sigma} [\text{K}]$	$T_c^* [\text{K}]$
A	6.70	1.32	38.9	8.7
B	6.38	1.76	38.9	11.5

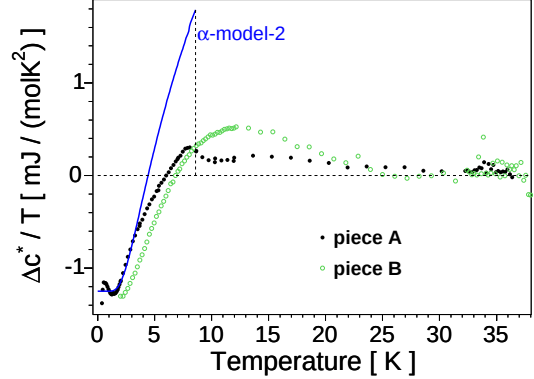


FIG. 6: (Color online) Electronic specific heat in the superconducting state which can be attributed to the π -electrons. The normal state and the contribution of the σ -band described by the α -model fitted to the jump have been subtracted. Filled circles: sample A. Open circles: sample B. Solid line marked by “ α -model-2”: α -model fitted to the low-temperature part of the small hump of piece A satisfying the condition of entropy-conservation.

heat analyses, which gave $\Delta_\pi(0) = 1.7 - 2.2 \text{ meV}$.^{19,22,24} It is interesting to compare the small gap of sample A with that of sample B. The open circles in Fig. 6 show the remaining specific heat of sample B after subtracting an α -model, fitted in a similar way to the jump height (resulting in $\Delta_\sigma(0) = 6.38 \text{ meV}$ for the larger gap). A fit of another α -model to the low-temperature part of $\Delta c^*/T$ (not shown here) as it was done for sample A, results in $\Delta_\pi(0) = 1.76 \text{ meV}$ for the small gap. A successful fit also requires a larger $T_c^* = 11.5 \text{ K}$ for this sample, comparable to $T_c^* \approx 11 \text{ K}$ reported by Bouquet et al.²² The smaller gap found for the π -band of sample A supports the scenario of a reduced inter-band coupling in this sample.¹⁶ The gap parameters are summarized in Tab. II.

In Fig. 7, the electronic specific heat of the σ - and the π -band in the superconducting state are compared. The left panel shows the specific heat data normalized on $T_{c,\sigma}$ and $\gamma_{N,\sigma}$ of the σ -band. The right panel shows the remaining electronic specific heat as given in Fig. 6 (plus $\gamma_{N,\pi}$) normalized on T_c^* and $\gamma_{N,\pi}$ of the π -band. The deviation for $T_c^*/T > 4.5$ between the data and the corresponding α -model is due the mentioned uncertainty of the Schottky contribution (see also Fig. 6).

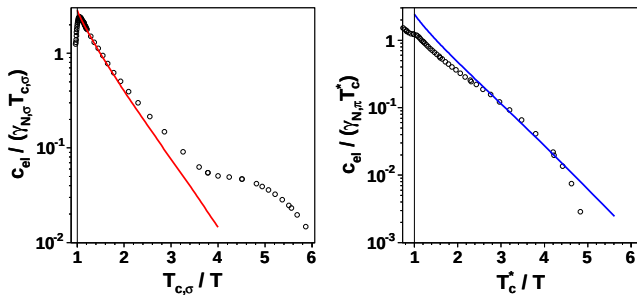


FIG. 7: (Color online) Normalized electronic specific heat of sample A. Left panel: experimental electronic specific heat of the superconducting state. Solid line: α -model according to Fig. 4. Right panel: remaining electronic specific heat attributed to the π -band, normalized on $T_c^* = 8.7$ K. Solid line: α -model according to Fig. 6.

C. Field-dependence of the specific heat below 15 K

In order to clarify the nature of the hump found in the electronic specific heat in the superconducting state near 8 K, specific heat measurements in applied magnetic fields between $\mu_0 H = 0.1$ and 9.0 T have been performed. The resulting specific-heat-to-temperature-ratio is shown in Fig. 8. The shaded area marks the temperature region of the anomaly for the zero-field measurement as shown in Fig. 4. Two properties of the anomaly can be derived from these measurements. First, the position of the anomaly is more or less unchanged. Second, the anomaly is flattened out with increasing magnetic field, accompanied by an increase of the specific heat at low temperatures. The anomaly vanishes at approximately 9 T, where the superconducting signal of the specific heat is very hard to separate, indicating that the origin of the anomaly is connected to the superconductivity of Mg^{10}B_2 . Comparing the hump qualitatively with recent calculations performed by Nicol and Carbotte,¹⁶ it seems that the inter-band coupling in our sample is reduced by $\approx 30 - 50$ % compared to previously reported samples (see section IV for a detailed analysis). The inter-band coupling can therefore be expected to be in the order of ≈ 0.2 . Comparing the specific heat measurements of Bouquet et al.²² and Wang et al.,²⁴ as was done in Ref. 26 it is obvious that it is possible to vary the inter-band coupling, probably by means of the preparation technique. In particular the low temperature anomaly in the data of Bouquet et al. is much more pronounced than in the data of Wang et al., but there is no upturn visible as in our sample (A).

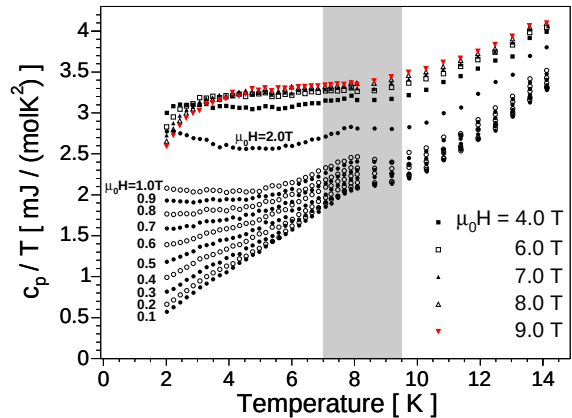


FIG. 8: (Color online) Specific heat c_p/T in different applied magnetic fields as labeled. The vicinity of the upturn observed in the zero-field measurement is marked by the shaded area.

IV. DISCUSSION

Both gap values for sample A, $\Delta_\sigma(0) = 6.70$ meV and $\Delta_\pi(0) = 1.32$ meV are in the lower region of the expected values for MgB_2 .¹² In general, specific heat measurements are expected to result in averaged gap values, resulting from the two bands. On the other hand, transport measurements like point-contact spectroscopy measurements are also influenced by the Fermi velocity distribution of the charge carriers of the individual bands, usually resulting in gap values from the faster charge carriers of the two bands. A comparison with calculations by Choi et al.¹³ shows that the present gap values represent the lower end of the calculated gap distribution.

Additional information on the electron-phonon coupling can be derived by comparing the resulting thermodynamic quantities with band-structure results. For this purpose we make use of a strong coupling correction term given by Carbotte:²⁷

$$\frac{\Delta c}{\gamma_N T_c} = 1.43 \left(1 + \frac{53}{x^2} \ln \frac{x}{3} \right)$$

with $x = \omega_{\text{ln}}/T_c$. Analyzing the jump with $T_{c,\sigma}$ and $\gamma_{N,\sigma}$ in this manner, the characteristic phonon frequency amounts to $\omega_{\text{ln},\sigma} = 712$ K. Using the McMillan formula (refined by Allen and Dynes²⁸):

$$T_c = \frac{\omega_{\text{ln}}}{1.2} \exp \left[-\frac{1 + \lambda_{\text{ph}}}{\lambda_{\text{ph}} - \mu^* (1 + 0.6 \lambda_{\text{ph}})} \right], \quad (3)$$

with the Coulomb pseudopotential $\mu^* = 0.10$, one finds $\lambda_{\text{ph},\sigma} = 0.82$. With $\gamma_{N,\sigma} = 1.44$ mJ/(molK²) one gets $\gamma_{0,\sigma} = 0.79$ mJ/(molK²) for the bare electron parameter of the σ -band. With $\gamma_0 = 1.67$ mJ/(molK²), the bare electron parameter for the π -band amounts to

TABLE III: Parameters characterizing the electron-phonon coupling. The first two columns contain calculated values²⁹. The characteristic phonon frequencies have been calculated by integrating the corresponding Eliashberg functions in Ref. 29. T_c was calculated using Eq. (3) with $\mu^* = 0.1$ (thereby ignoring all inter-band effects). The next two columns show the present experimental results for sample A.

		theoretical –		experimental values	
		π	σ	π	σ
ω_{ln}	[K]	668	770	1270	712
λ_{ph}		0.45	1.02	0.42	0.82
T_c	[K]	6.25	59.33	8.7	38.9

$\gamma_{0,\pi} = \gamma_0 - \gamma_{0,\sigma} = 0.88 \text{ mJ}/(\text{molK}^2)$. The electron-phonon coupling within the π -band can then be estimated from the mass enhancement (Eq. 1) as $\lambda_{\text{ph},\pi} = \gamma_{N,\pi}/\gamma_{0,\pi} - 1 = 0.42$. The corresponding characteristic phonon frequency determined from Eq. (3) amounts to $\omega_{\text{ln},\pi} = 1270 \text{ K}$. It can only be guessed whether this rather large value is related to the mentioned anharmonic effects seen in the specific heat at large temperatures or inaccuracies of the band structure calculations. From this analysis the σ -band contributes with $\approx 47 \%$ and the π -band with $\approx 53 \%$ to the total density of states. Setting the derived parameters in Eq. (2), one confirms the value of $\bar{\lambda}_{\text{ph}} = 0.61$. The obtained results are summarized in Tab. III in comparison with calculated values derived by analyzing theoretical Eliashberg functions.²⁹

A nice check of the obtained parameters can be performed by analyzing the deviation function $D(t)$ given by (see for example Ref. 30):

$$D(t) = \frac{H_c(T)}{H_c(0)} - (1 - t^2),$$

with $t = T/T_c$ (in the following $T_c = T_{c,\sigma}$ is used). It gives the deviation from the two-fluid model of the superconducting state, thus revealing important information on the superconducting state. Fig. 9(a) shows that $D(t)$ of Mg^{10}B_2 (sample A) closely resembles the BCS prediction, in particular near T_c . However, there are some deviations from this behavior. First the minimum is shifted to lower temperatures and second, the behavior for $T \rightarrow 0$ strongly deviates from the BCS prediction.

Based on the weak-coupling two-band equations derived by Moskalenko and Palistrant³¹ and by analyzing numerical data given in Ref. 27 we derived an analytical expression for $D(t)$, describing deviations due to two-band influences. Within the BCS theory the dependence of the thermodynamic critical field for $T \rightarrow 0$ is given by

$$\left[\frac{H_c(T)}{H_c(0)} \right]^2 = 1 - 2.12\beta \left(\frac{T}{T_c} \right)^2, \quad (4)$$

with $\beta \approx 1$. In the case of increasing electron-phonon coupling β is decreasing but it is increasing again in the case of two-band influence with different gaps in both

bands. In this case β can be expressed as

$$\beta = z \frac{B\left(\frac{\omega_{\text{ln},\sigma}}{T_c}\right) + B\left(\frac{\omega_{\text{ln},\pi}}{T_c}\right)}{z^2 + v} \exp\left[\frac{z^2 - v}{z^2 + v} \ln(z)\right], \quad (5)$$

with

$$\begin{aligned} z &= \frac{\Delta_\sigma(0)}{\Delta_\pi(0)}, \\ v &= \frac{(1 + \lambda_{\text{ph},\pi}) N_\pi(0)}{(1 + \lambda_{\text{ph},\sigma}) N_\sigma(0)}, \\ B(x) &= 1 - \frac{7.5}{x^2} \ln \frac{x}{3}. \end{aligned}$$

Eq. (5) corresponds to the BCS limit for the weak-coupling single-band case and reproduces the strong coupling corrections reported by Carbotte.²⁷ The agreement of Eq. (5) with the two-band Eliashberg theory was checked numerically for the theoretical case given by Golubov et al.,²⁹ where the deviation is found to be less than 4 %.²⁵ Parameters obtained from these calculations are given in Tab. III. Using the above derived electron-phonon coupling quantities and $T_c = T_{c,\sigma}$, one derives $\beta = 1.56$. The dependence of $D(t)$ at low temperatures is plotted in Fig. 9(b), showing the very nice agreement of this analytical formula with the experimental deviation function.

However, Fig. 9(c) shows that the deviation function of the present sample A (filled circles) looks quite different from that of sample B (open squares). For the data of Bouquet et al.²² a minimum value of $\approx 5.5 \%$ was determined,¹⁶ similar to sample B, but sample A has a minimum value of only $\approx 3.5 \%$.

It is interesting to compare these data to Eliashberg-model calculations. Nicol and Carbotte recently published such calculations where they varied the inter-band coupling, using the standard set of $\lambda_{\sigma\pi} = 0.213$ and $\lambda_{\pi\sigma} = 0.155$ and a second set with halved inter-band λ -values. Fig. 9(c) shows the comparison between these calculations and our data. From that it can be concluded, that the inter-band coupling in sample A is reduced compared to that of sample B by approximately 30 %.

Fig. 10 shows a comparison between the electronic specific heat below T_c for the investigated two samples and the calculations by Nicol and Carbotte [which correspond to Fig. 9(c)]. There is a qualitative agreement between the data sets and the calculations except for the vicinity of T_c , where the calculations predict a reduction of the normalized jump with decreasing inter-band coupling. In addition there is no increase of T_c for the sample with the stronger inter-band coupling. However, Nicol and Carbotte showed that for some combinations of $\lambda_{\pi\sigma}$ and $\lambda_{\sigma\pi}$, even a decrease of T_c is possible.¹⁶ Therefore it seems difficult to make predictions concerning T_c or the jump.

The question, why two samples of the same initial piece should have different values of the inter-band coupling constants is still unsolved. In the present case it

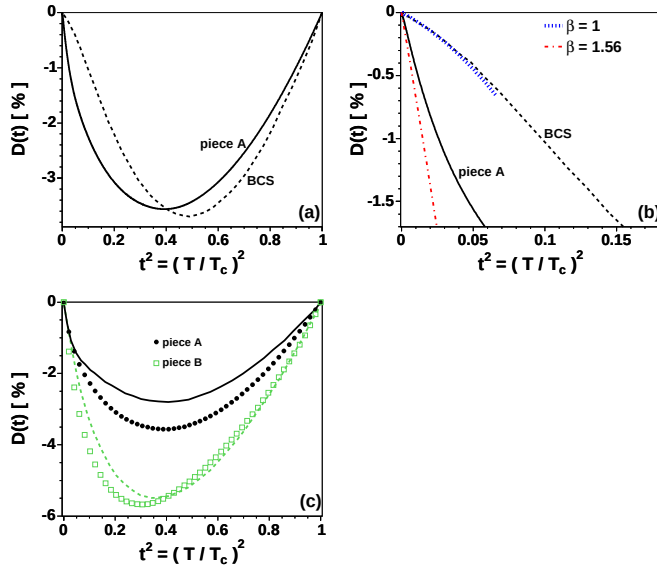


FIG. 9: (Color online) Experimental deviation function $D(t)$ compared to model predictions. (a) and (b): $D(t)$ of sample A compared to the BCS-model prediction. Dotted line in (b): Eq. (4) with $\beta = 1$ (BCS case). Dash-dotted line in (b): Eq. (4) with β recalculated according to Eq. (5), using the experimentally derived values. (c): Comparison of $D(t)$ of both samples with Eliashberg-model calculations taken from Ref. 16. Dashed line: calculation using “normal” inter-band coupling. Solid line: calculation with 50 % reduced inter-band coupling.

is most probably related to different amounts of impurities, which influence the inter-band coupling by local lattice distortions. These lattice distortions can modify the electron-phonon coupling. Therefore it is also difficult to draw conclusions from the Sommerfeld parameter, which is at the same time determined by the two intra-band and inter-band coupling constants.

V. CONCLUSION

In the present work we report the first detailed specific heat analysis of a MgB_2 -sample with a particularly low inter-band coupling. The observed low-temperature upturn within the superconducting state is in accord with theoretical studies.¹⁶ It is shown, that just by using results of band-structure calculations, meaningful physical quantities can be derived from specific heat measurements. The relatively low gap values, $\Delta_\sigma(0) = 6.38$ meV and $\Delta_\pi(0) = 1.76$ meV of sample B, which represents a “standard” MgB_2 -sample, naturally emerge from the type of measurement. Transport measurements usually result in higher values of the gaps, indicating that the gap val-

ues depend on the velocity of the charge carriers, again raising the question, if a gap distribution within the two bands as calculated by Choi et al. can become experi-

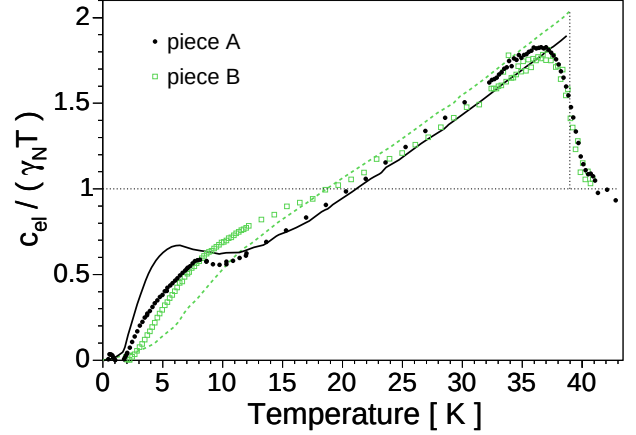


FIG. 10: (Color online) Electronic specific heat $c_{el}/\gamma_N T$ of both samples compared to Eliashberg-calculations by Nicol and Carbotte.¹⁶ The dashed and solid lines correspond to the lines in Fig. 9(c).

mentally visible.^{6,13,32,33} The resulting electron-phonon coupling constants for sample A show, that the σ -band couples stronger than the π -band, as expected, but still Mg^{10}B_2 can be considered as a weak to medium coupling superconductor. Thus, the large characteristic phonon frequency is the main reason for the relatively large superconducting transition temperature, showing the crucial role of the E_{2g} -mode. The obtained parameters for sample A were found to be in agreement with the low temperature behavior of the deviation function $D(t)$. Comparing the deviation function and the electronic specific heat of the superconducting state of both samples with calculations by Nicol and Carbotte, the scenario of a low inter-band coupling for the present sample A is supported. This is in particular agreeing well with the ≈ 30 % smaller gap within the π -band of that sample. This reduction was predicted theoretically in the case of a reduced inter-band coupling constant by ≈ 30 %.¹⁶ However sample B from the same initial piece does not show this peculiarity. At present it is still unclear, which parameter in the sample preparation process controls the inter-band coupling.

Acknowledgments

The DFG (SFB 463) is gratefully acknowledged for financial support. We thank S. V. Shulga for fruitful discussions.

-
- * Electronic address: waelte@ifw-dresden.de
- ¹ J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, and J. Akimitsu, *Nature* **410**, 63 (2001).
 - ² J. M. An and W. E. Pickett, *Phys. Rev. Lett.* **86**, 4366 (2001).
 - ³ Y. Kong, O. V. Dolgov, O. Jepsen, and O. K. Andersen, *Phys. Rev. B* **64**, 020501(R) (2001).
 - ⁴ A. Y. Liu, I. I. Mazin, and J. Kortus, *Phys. Rev. Lett.* **87**, 087005 (2001).
 - ⁵ J. Kortus, I. I. Mazin, K. D. Belashchenko, V. P. Antropov, and L. L. Boyer, *Phys. Rev. Lett.* **86**, 4656 (2001).
 - ⁶ H. J. Choi, D. Roundy, H. Sun, M. L. Cohen, and S. G. Louie, *Phys. Rev. B* **66**, 020513(R) (2002).
 - ⁷ K.-P. Bohnen, R. Heid, and B. Renker, *Phys. Rev. Lett.* **86**, 5771 (2001).
 - ⁸ T. Yildirim, O. Gülseren, J. W. Lynn, C. M. Brown, T. J. Udovic, Q. Huang, N. Rogado, K. A. Regan, M. A. Hayward, J. S. Slusky, et al., *Phys. Rev. Lett.* **87**, 037001 (2001).
 - ⁹ R. Osborn, E. A. Goremychkin, A. I. Kolesnikov, and D. G. Hinks, *Phys. Rev. Lett.* **87**, 017005 (2001).
 - ¹⁰ A. Shukla, M. Calandra, M. d'Astuto, M. Lazzeri, F. Mauri, C. Bellin, M. Krisch, J. Karpinski, S. M. Kazakov, J. Jun, et al., *Phys. Rev. Lett.* **90**, 095506 (2003).
 - ¹¹ R. Heid, B. Renker, H. Schober, P. Adelmann, D. Ernst, and K.-P. Bohnen, *Phys. Rev. B* **67**, 180510(R) (2003).
 - ¹² I. K. Yanson and Y. G. Naidyuk, *Low Temp. Phys.* **30**, 261 (2004).
 - ¹³ H. J. Choi, D. Roundy, H. Sun, M. L. Cohen, and S. Louie, *Nature* **418**, 758 (2002).
 - ¹⁴ I. I. Mazin and V. P. Antropov, *Physica C* **385**, 49 (2003).
 - ¹⁵ O. V. Dolgov, R. Kremer, J. Kortus, A. A. Golubov, and S. V. Shulga, *Phys. Rev. B* **72**, 024504 (2005).
 - ¹⁶ E. J. Nicol and J. P. Carbotte, *Phys. Rev. B* **71**, 054501 (2005).
 - ¹⁷ S. L. Bud'ko, G. Lapertot, C. Petrovic, C. E. Cunningham, N. Anderson, and P. C. Canfield, *Phys. Rev. Lett.* **86**, 1877 (2001).
 - ¹⁸ D. K. Finnemore, J. E. Ostenson, S. L. Bud'ko, G. Lapertot, and P. C. Canfield, *Phys. Rev. Lett.* **86**, 2420 (2001).
 - ¹⁹ R. A. Fisher, G. Li, J. C. Lashley, F. Bouquet, N. E. Phillips, D. G. Hinks, J. D. Jorgensen, and G. W. Crabtree, *Physica C* **385**, 180 (2003).
 - ²⁰ N. A. Frederick, S. Li, M. B. Maple, V. F. Nesterenko, and S. S. Indrakanti, *Physica C* **363**, 1 (2001).
 - ²¹ A. Wälte, G. Fuchs, K.-H. Müller, S.-L. Drechsler, K. Nenkov, and L. Schultz, *Phys. Rev. B* **72**, 100503(R) (2005).
 - ²² F. Bouquet, R. A. Fisher, N. E. Phillips, D. G. Hinks, and J. D. Jorgensen, *Phys. Rev. Lett.* **87**, 047001 (2001).
 - ²³ H. D. Yang, J.-Y. Lin, H. H. Li, F. H. Hsu, C. J. Liu, S.-C. Li, R.-C. Yu, and C.-Q. Jin, *Phys. Rev. Lett.* **87**, 167003 (2001).
 - ²⁴ Y. Wang, T. Plackowski, and A. Junod, *Physica C* **355**, 179 (2001).
 - ²⁵ S. V. Shulga, *to be published*.
 - ²⁶ F. Bouquet, Y. Wang, R. A. Fisher, D. G. Hinks, J. D. Jorgensen, A. Junod, and N. E. Phillips, *Europhys. Lett.* **56**, 856 (2001).
 - ²⁷ J. P. Carbotte, *Rev. Mod. Phys.* **62**, 1027 (1990).
 - ²⁸ P. B. Allen and R. C. Dynes, *Phys. Rev. B* **12**, 905 (1975).
 - ²⁹ A. A. Golubov, J. Kortus, O. V. Dolgov, O. Jepsen, Y. Kong, O. K. Andersen, B. J. Gibson, K. Ahn, and R. K. Kremer, *J. Phys.: Condens. Matter* **14**, 1353 (2002).
 - ³⁰ C. P. Poole, H. A. Farach, and R. J. Creswick, *Superconductivity* (Academic Press, 1995), ISBN 0-1256-1455-1.
 - ³¹ V. A. Moskalenko and M. E. Palistrant, *Theory of pure two-band superconductors*, Statistical Physics and Quantum Field Theory (Nauka, Moskau, 1973).
 - ³² I. I. Mazin, O. K. Andersen, O. Jepsen, A. A. Golubov, O. V. Dolgov, and J. Kortus, *Phys. Rev. B* **69**, 056501 (2004).
 - ³³ H. J. Choi, D. Roundy, H. Sun, M. L. Cohen, and S. G. Louie, *Phys. Rev. B* **69**, 056502 (2004).